


BA10 (Bone ash)

14.0

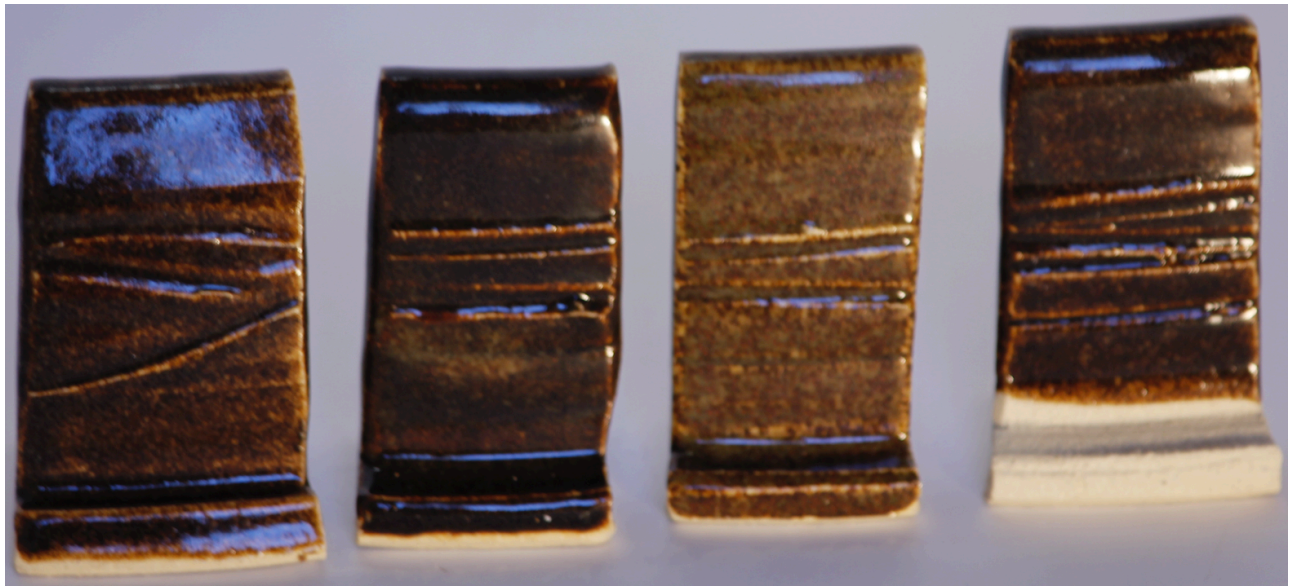

	100	100	100
Silica	33	20	25
Kaolin (EPK)	11	8	7
Ball Clay (OM4)		7	
Potash Feldspace (Cluster)		32	10
Nepheline Syenite	22		20
Talc	5	5	8
Gerstley Borate (Laguna)		8	20
Frit 3134	19	10	
Bone Ash	10	10	10
(KNa)O [0.1 to 0.3]	0.268	0.249	0.204
MgO [0 to 0.3]	0.139	0.163	0.237
CaO [0.2 to 0.6]	0.593	0.587	0.556
ZnO [0 to 0.20]			
Al ₂ O ₃ [0.25 to 0.5]	0.312	0.352	0.267
B ₂ O ₃ [0 to 0.3]	0.214	0.208	0.203
SiO ₂ [0.25 to 0.4]	3.565	3.247	2.591
Si:Al	11.43	9.23	9.71

Notes:

- #1 modification of Snowy Lilac base
- #2 modification of Whiskey Rive base
- #3 cross of chocolate matte and zam celedon

Results with 5% synthetic red iron oxide (high purity)

- #1 lightly glossy, slightly mottled with spots of red
- #2 rich brown, medium gloss, creamy green in places (my favorite)
- #3 very mottled camo green and brown with red specks
- mix: nothing overly special