


BA3 Iron-Cobalt

14.4

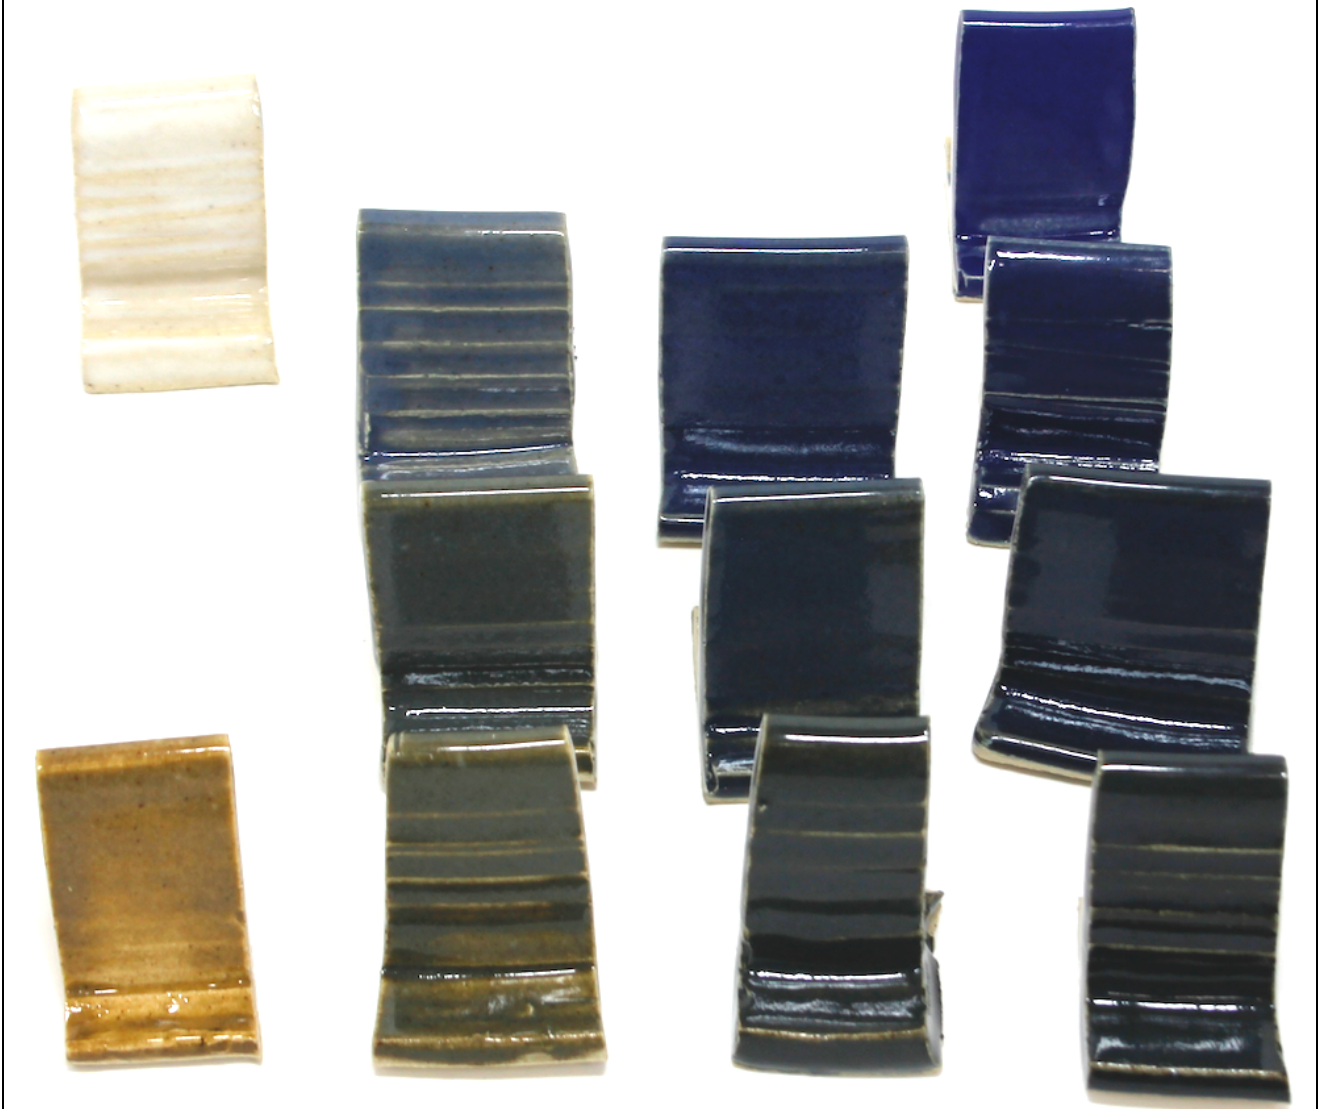

BA3

Silica	25
Kaolin (EPK)	7
Potash Feldspace (Cluster)	10
Nepheline Syenite	20
Talc	8
Gerstley Borate (Laguna)	20
Bone Ash	10

Iron Oxide (Spanish) 0, 1.3, 2.6, 4 top to bottom

Cobalt Carbonate 0, 0.66, 1.33, 2 left to right

Base glaze (top left) is very milky, glossy, shows signs of coarse crazing.

The most interesting region appear around 1-3% iron and 0.5-1.5% cobalt. This is resulting in deep indigo colors similar to cobalt glazes on iron bodies.

The 4% iron and 1-2% cobalt appears almost perylene green.