


# PBR variations

4.1

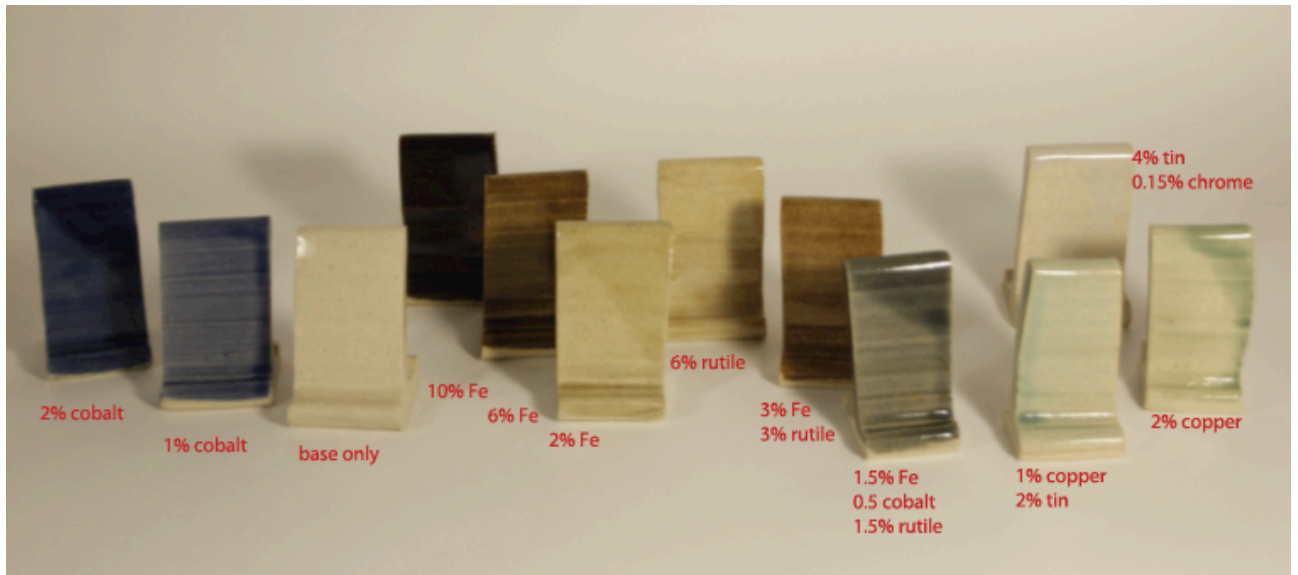

	PBR 1	PBR 2
Silica	33	33
Kaolin (EPK)	11	14
G. Borate	9	10
Talc	2	7
Whiting	16	6
Neph Sy	16	18
Pot Feld	15	6
Frit 3134		6
Rutile (milled)	2	2

**Notes:**

Picture of PBR 2 color test. 2% was replaced with listed colors.

The base glaze has the potential to be a high quality clear.  
Addition of cobalt gave an excellent royal blue.

The response to iron was neutral.

The 6% rutile version gives a nice nutmeg; may be worth exploring further.

The chrome-tin did not produce signs of pink.

The 2% is a normal green. The addition of tin creates a rather pleasant light blue.

A variation of this glaze became "Melting Glacier"