


# PMgO (Magnesium Purple) Test

5.2

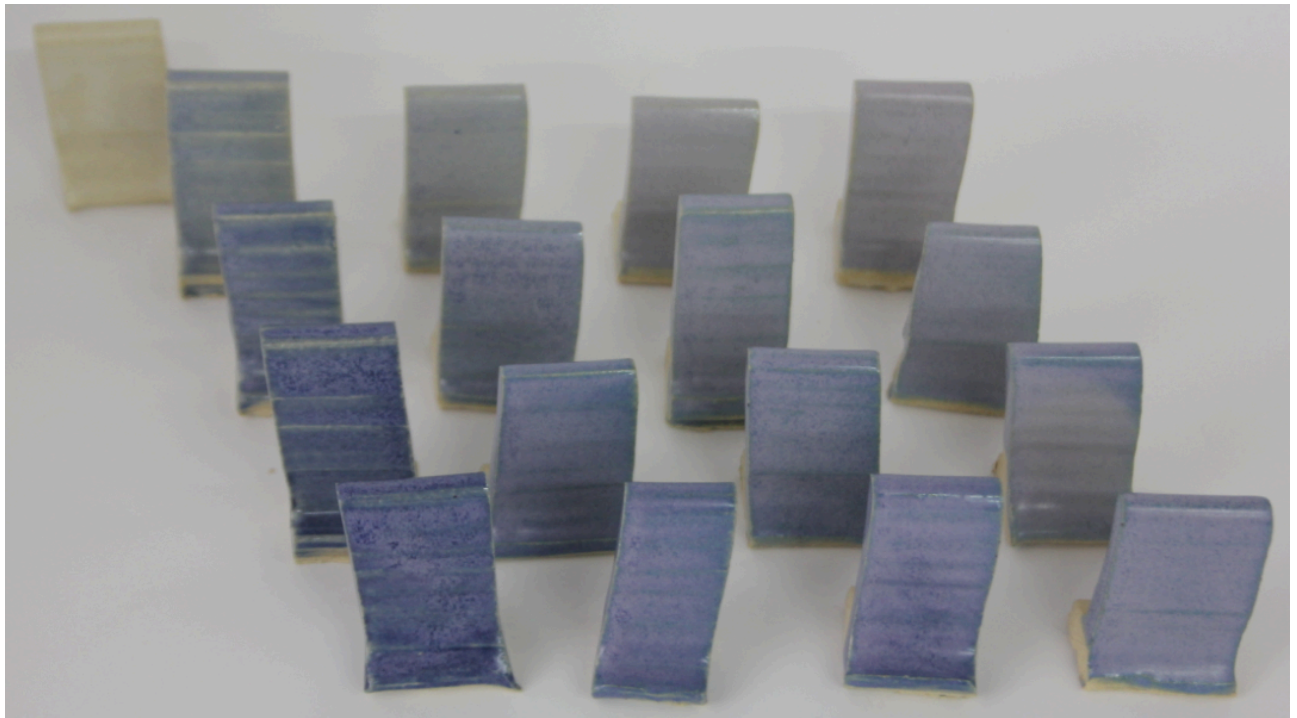

P5

Silica 31

Kaolin (EPK) 10

Nepheline Syenite 21

Whiting 11

G. Borate 19

Talc 8

4.2 Tin Oxide  
0.15 Chrome premix 2, 4, 6, 8 left the right

Cobalt Carbonate 0.25, 0.5, 0.75, 1 top to bottom

Notes:

Top left, no colorants added. Surface is a milky satin matte  
Across: 2, 4, 6, 8 of (4.2 Tin Oxide : 0.15 Chrome Oxide premix)  
Down: 0.25, 0.5, 0.75, 1.0 of Cobalt Carbonate

My preference was for (4 Tin+Chrome, 1 Cobalt) and (4 Tin+Chrome, 0.25 Cobalt)

This is the same base as "White Lilac" which is colored with just 4 Tin+Chrome. A more pronounced lilac could be made with ~0.1 Cobalt added to it.