


# “Snowy Lilac” Base (iron-rutile) Test

5.5

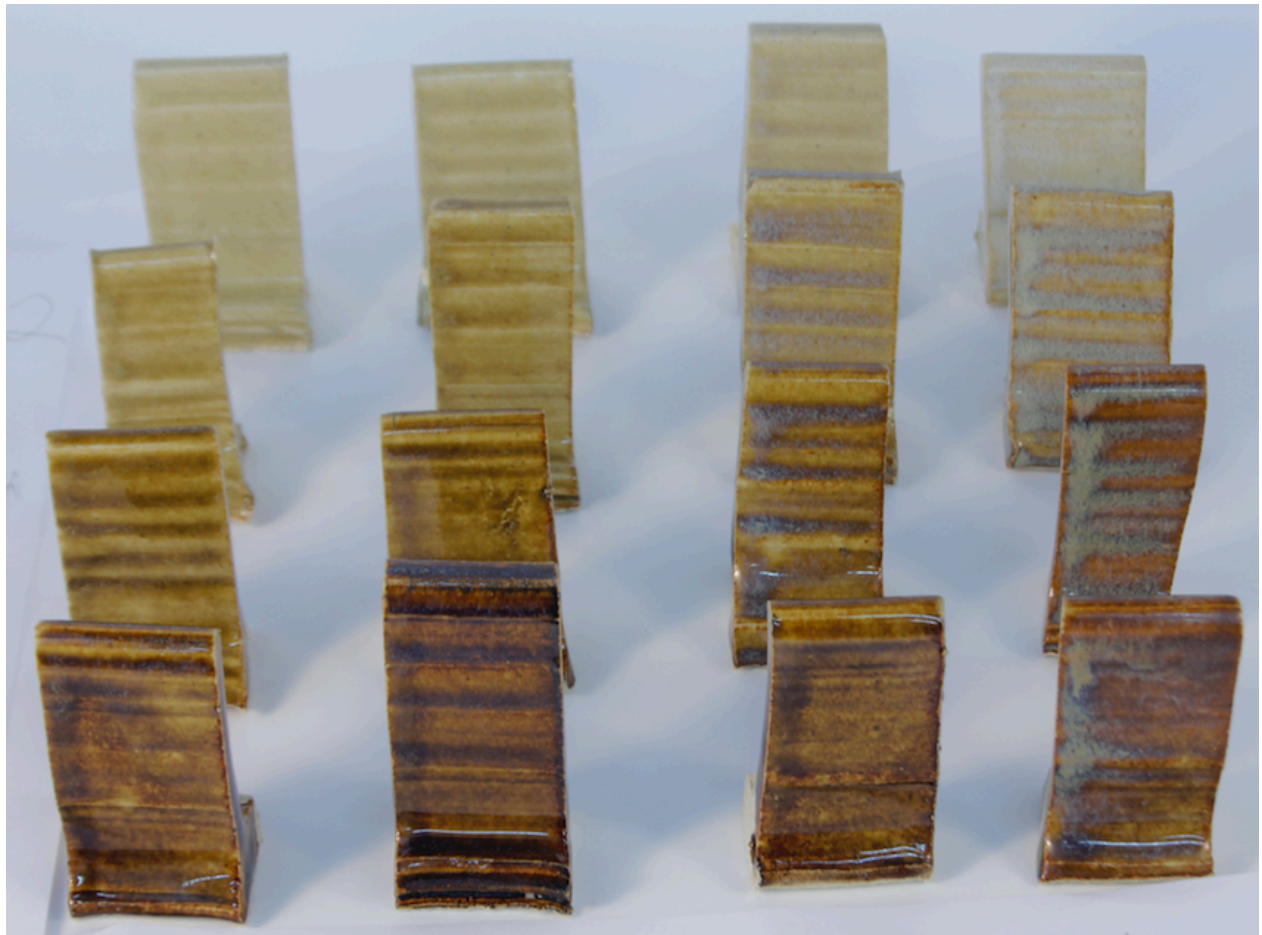

Base	
Silica	31
Kaolin (EPK)	10
Nepheline Syenite	21
Whiting	11
G. Borate	19
Talc	8
Iron oxide (Spanish Red)	2, 4, 6, 8 top to bottom
Rutile (milled)	1, 2, 3, 4 left to right

**Notes:**

Not pictured: no colorants added surface is a milky satin matte.

This is the same base as “Snowy Lilac” which is colored with 4 Tin, 0.1 cobalt carbonate.

The tests with high levels of rutile have good verigation.

The 4 iron, 3 rutile test has a good balance of light base color and a quiet surface finish.

The 8 iron, 4+ rutile would make a stunning flowing blue.

An excellent honey glaze could be made from ~6 iron and 1 or less rutile.