


ZB#2 copper-iron

7.1

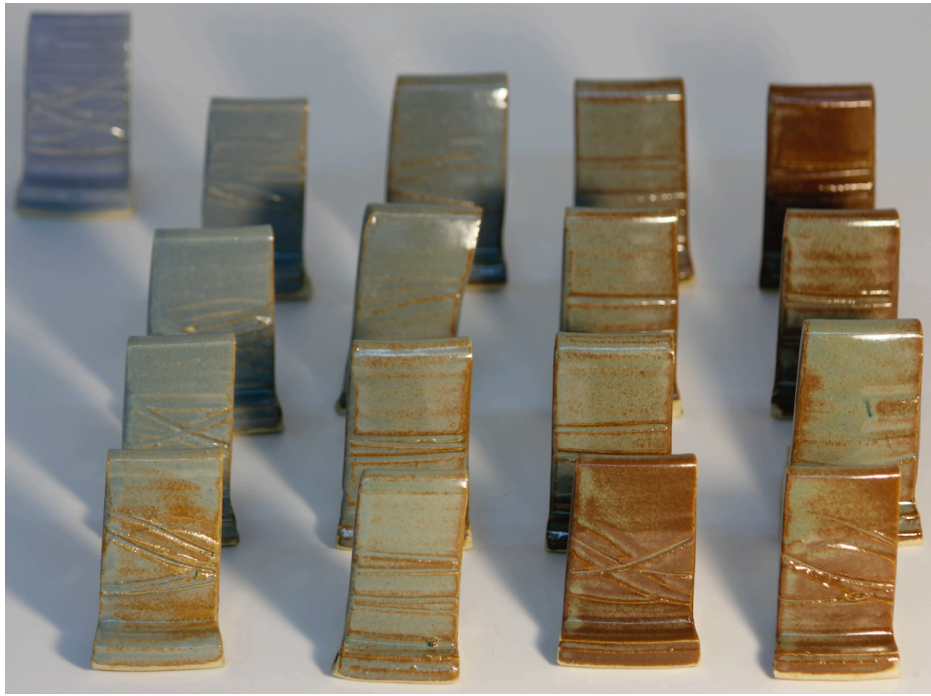

	100
Silica	18
Wollastonite	15
Potash Feldspar (Cluster)	30
Ball Clay (OM4)	10
Zinc Oxide	11
Nepheline Syenite	4
G. Borate	12
Rutile (milled)	4
Cobalt Carbonate	0.5
Copper Carbonate	0.5, 1.0, 1.5, 2.0 top to bottom
Red Iron Oxide (Spanish)	1, 2, 3, 4 left to right
<p>Notes:</p> <p>The goal of this test was to create a rich blue-green “sage” glaze. 4% rutile and 0.5% cobalt carbonate were added to the base mixture.</p> <p>The variation of iron had a much larger influence on the glaze. The 2% (2nd column) was generally the most pleasant without being overpowering.</p> <p>The copper level was less noticeable. About 1% seemed to be the best amount overall.</p>	